



Cite this: *Chem. Commun.*, 2015, 51, 15932

Received 6th August 2015,
Accepted 4th September 2015

DOI: 10.1039/c5cc06595j

www.rsc.org/chemcomm

Separation of cobalt and nickel using a thermomorphic ionic-liquid-based aqueous biphasic system†

Bieke Onghena, Tomas Opsomer and Koen Binnemans*

A [P₄₄₄₁₄][Cl]–NaCl–H₂O ionic liquid-based aqueous biphasic system shows promising results for the separation of cobalt(II) and nickel(II) by homogeneous liquid–liquid extraction. The extracting phase consists of a hydrophilic ionic liquid that is salted-out by sodium chloride, indicating that there is no need for using hydrophobic ionic liquids.

Recent advances in sustainable hydrometallurgical processing of metals focus on the use of hydrophobic ionic liquids (ILs) for separation of metal ions by solvent extraction.^{1–4} Ionic liquids are solvents that consist entirely of ions. Because of their low flammability and low volatility, ILs are considered to be safer and more environmentally friendly than the traditional diluents that are currently used in industry, such as kerosene.^{4–7} The main disadvantage of using ILs in solvent extraction is their high viscosity, which slows down the mass transfer during extraction and complicates the implementation of the IL solvent extraction processes on an industrial scale.⁸ Recently, our group applied the concept of homogeneous liquid–liquid extraction (HLL) to ionic liquids as an answer to the slow mass transfer caused by the high viscosities of ILs. HLL makes use of thermomorphic ILs, *i.e.* ILs that show temperature-dependent phase behavior in contact with water.^{9–11} Reversible conversion of the biphasic mixture to a homogeneous mixture by changing the temperature causes the extraction equilibrium to be reached faster than by strong agitation of a biphasic mixture. Until now, mainly fluorine-containing ILs were successfully applied to the HLL of metal ions.^{12–14} On the other hand, ILs with fluorine-free anions offer several advantages such as lower price and less issues with toxicity and persistency in natural environments.^{15,16} Fluorine-free hydrophobic ILs, such as trihexyl(tetradecyl)phosphonium chloride (Cyphos IL 101), have already been used in solvent extraction processes, but these ILs generally do not show thermomorphic behavior with

water and hence cannot be used in HLL.^{13,20–28} Furthermore, they have a high viscosity, which makes their application in industrial solvent extraction less straightforward.

In this Communication, the assets of both HLL and fluorine-free ILs for the separation of metal ions are combined by using thermomorphic ionic liquid–salt aqueous biphasic systems (IL-ABSs) in HLL. An IL-ABS usually consists of three components: (1) water; (2) a hydrophilic IL, preferably with a fluorine-free cation; and (3) a salting-out agent, usually an inorganic salt. The salting-out agent causes the IL to phase separate from the mixture and a biphasic system is created.^{17–19} Phase separation is thus a composition-induced process (CIPS, composition-induced phase separation). At certain mass compositions, many of the IL-ABSs can also undergo temperature-induced phase separation (TIPS), thus they can be considered thermomorphic and applicable to HLL.^{17,20,21} Despite the advantages, few examples of the use of IL-ABSs for the extraction of metal ions have been reported in the literature. Furthermore, the thermomorphic behavior has not been exploited yet.^{18,22–25}

Here, the concept of using IL-ABS-HLL for the separation of metals was applied to the separation of cobalt(II) and nickel(II) using the hydrophilic IL tributyl(tetradecyl)phosphonium chloride, [P₄₄₄₁₄][Cl], combined with NaCl as the salting-out agent. NaCl was selected for several reasons: (1) NaCl is cheap and easily available with a low impact on the environment; (2) it is a relatively good salting-out agent; and (3) the addition of chloride ions enhances the extraction of anionic metal chloro complexes to the IL phase.^{26,27} Extraction using [P₄₄₄₁₄][Cl] is similar to Cyphos IL 101 since both ILs are anionic extractants, which means that they only extract metal ions in their anionic form, such as anionic tetrachlorocobaltate(II).^{27,28}

To examine the possibility of using [P₄₄₄₁₄][Cl] in an IL-ABS-HLL system, the phase behavior and phase separation were first investigated as a function of temperature and NaCl concentration. By cloud point titration at room temperature, the concentration of NaCl required to induce phase separation was determined for different IL concentrations (expressed in wt%) (Fig. S1 in the ESI†). The cloud-point composition, *i.e.* the composition at

KU Leuven, Department of Chemistry, Celestijnenlaan 200F PO box 2404, Leuven, 3001 Heverlee, Belgium. E-mail: Koen.Binnemans@chem.kuleuven.be

† Electronic supplementary information (ESI) available: Experimental information, the orthogonal ternary phase diagram of the [P₄₄₄₁₄][Cl]–NaCl–H₂O system and the quantitative ¹NMR spectrum. See DOI: 10.1039/c5cc06595j

which the homogeneous mixture becomes cloudy, was determined by titrating an aqueous solution of NaCl against an aqueous solution of the IL under constant stirring until a cloudy solution was detected visually. On the basis of these results, it was decided to carry out further experiments with mixtures always containing 40 wt% of IL. In this way, the required amount of NaCl to obtain phase separation at room temperature was still limited (around 5 wt%, Fig. S1 in the ESI†) and the mass phase ratio of the biphasic mixture was around 1:1. A complete overview of the experimental methods and materials is given in the ESI.†

Preliminary heating and cooling tests revealed that $[P_{44414}][Cl]$ -NaCl-H₂O showed a lower critical solution temperature (LCST) phase behavior in water, which implies that a biphasic mixture becomes homogeneous by cooling below a certain temperature. The temperature at which this phase transition occurs can be approximated by the cloud point temperature, which is literally the temperature at which a homogeneous mixture becomes cloudy at a specific composition, thus indicating a phase transition. The cloud point temperature of $[P_{44414}][Cl]$ -NaCl-H₂O was determined at different NaCl concentrations, expressed in wt% (Fig. 1). The results show that by changing the NaCl concentration the system parameters can be tuned very easily to optimize the process, which is interesting for the application in HLE. Note that at NaCl concentrations above 11 wt%, the mixture cannot become homogeneous by cooling since the cloud point temperature is below the melting point of water. This implies that HLE with a mixture containing 40 wt% of $[P_{44414}][Cl]$ in total is only possible at NaCl concentrations lower than 11 wt%.

Next, the $[P_{44414}][Cl]$ -NaCl-H₂O system was applied to the separation of Co(II) and Ni(II) from chloride solution by HLE. The separation of Co(II) and Ni(II) was chosen because it is an important but challenging hydrometallurgical process step in the production of cobalt materials.²⁹ Furthermore, they are known to be efficiently separated by traditional solvent extraction using quaternary phosphonium and ammonium ILs, but high viscosity remains a challenge in these systems.^{8,27} The extraction and separation of Co(II) and Ni(II) were tested as a function of the NaCl concentration (wt%) in the mixture (Fig. 2)

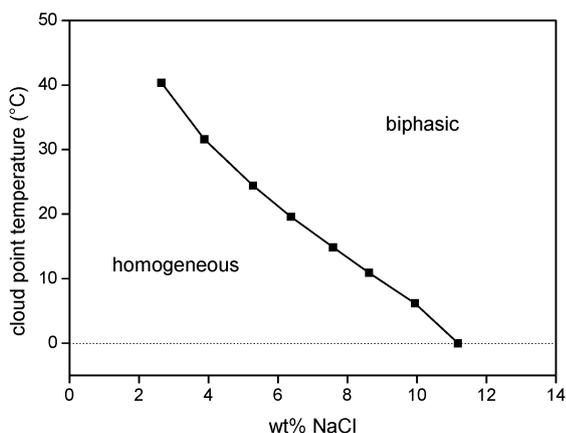


Fig. 1 Influence of the NaCl concentration on the cloud point temperature of a 40 wt% solution of $[P_{44414}][Cl]$ in water.

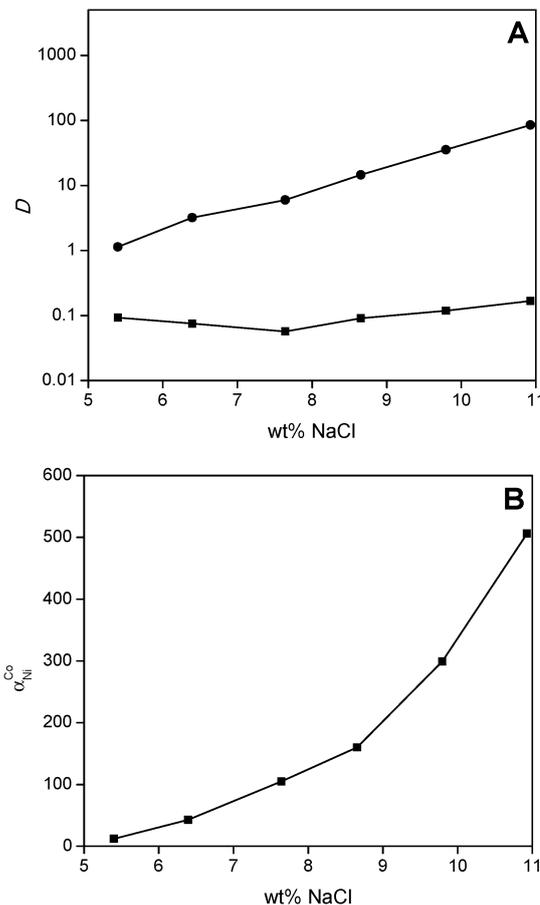


Fig. 2 (A) HLE of Ni(II) (■) and Co(II) (●) from chloride solution as a function of NaCl concentration (wt%) in the extraction mixture, (B) the corresponding separation factors α_{Ni}^{Co} . $[Co(II)] = 1 \text{ g kg}^{-1}$, $[Ni(II)] = 1 \text{ g kg}^{-1}$, and $[P_{44414}][Cl] = 40 \text{ wt\%}$, all calculated over the entire mixture.

and expressed using the distribution ratio D and separation factor α_{Ni}^{Co} , defined by eqn (1) and (2):

$$D = \frac{c_{IL}}{c_{aq}} \quad (1)$$

$$\alpha_{Ni}^{Co} = \frac{D_{Co}}{D_{Ni}} \quad (2)$$

where c_{aq} and c_{IL} are the metal concentrations after extraction in the aqueous and IL-rich phase, respectively.

The results showed that Ni(II) was only poorly extracted to the IL-rich phase ($D \sim 0.1$) and extraction was not improved by increasing the NaCl content in the mixture up to 11 wt%. On the other hand, Co(II) was extracted much better, with D values up to 100 at 11 wt% NaCl. This difference in extractability of Ni(II) and Co(II) at increasing NaCl concentration led to increasing separation factors up to 500 at 11 wt% of NaCl. As expected, the selectivity of extraction to the IL-rich phase is in line with the results obtained by Wellens *et al.* on the Cyphos IL 101 system and can be explained by the fact that Co(II) easily forms extractable anionic chloride complexes, while Ni(II) does not, not even at high chloride concentrations.²⁷ However, the distribution

Table 1 Influence of the wt% of NaCl in the [P₄₄₄₁₄][Cl]–NaCl–H₂O ABS mixture on the water content in the IL-rich phase determined by Karl Fischer titration and comparison with water-saturated Cyphos IL 101

	NaCl content in the mixture (wt%)	Water content in the IL-rich phase (wt%)
[P ₄₄₄₁₄][Cl]–NaCl–H ₂ O	5.4	24.8
	7.6	19.2
	9.8	15.5
	11.9	14.0
	13.1	12.9
Cyphos IL 101–H ₂ O	—	12.8 ^a
	—	7.7 ^b

^a Literature value, water-saturated Cyphos IL 101.³⁰ ^b Literature value, Cyphos IL 101 saturated with 8 M HCl.²⁷

ratios obtained with the IL-ABS-HLLE system are slightly lower than those obtained with the Cyphos IL 101 system because of the higher water content in the IL-rich phase (Table 1).^{27,30} The presence of water in the IL rich phase results in more physical resemblance between both phases, thus lowering the preferential distribution to the IL-rich phase.

The extraction of Co(II) and subsequent separation between Co(II) and Ni(II) was further improved by increasing the NaCl content in the mixture: $D_{Co} = 500$ and $\alpha_{Ni}^{Co} = 2500$ at 13 wt% NaCl. But, these mixtures with a composition of 40 wt% [P₄₄₄₁₄][Cl] and more than 11 wt% NaCl could no longer become homogeneous by changing the temperature, as also depicted in Fig. 1. However, the separation between Co(II) and Ni(II) with HLLE could be improved by optimizing the composition of the extraction mixture to increase the amount of NaCl that can be added. As indicated before, the amount of NaCl needed to induce phase separation is higher at lower IL content in the mixture (Fig. S1 in ESI†). This also means that at lower IL content in the mixture, the amount of NaCl that can be added to remain within the thermomorphic region is higher and higher separation factors α_{Ni}^{Co} could be obtained.

With respect to reusability and losses of the IL during the extraction process, it is important to know the IL content in the aqueous phase after extraction, since this value must be as low as possible to prevent unwanted losses. Quantitative ¹H NMR measurements were made to determine the IL concentration in the aqueous phase of an extraction mixture containing 40 wt% [P₄₄₄₁₄][Cl], 5.4 wt% NaCl, [Co(II)] = 1 g kg⁻¹ and [Ni(II)] = 1 g kg⁻¹. Phenol was added as internal standard, since the peak of its aromatic protons does not overlap with the resonances of water or the ionic liquid.³¹ The IL concentration was very low and close to the detection limit of the ¹H NMR measurement. By comparison with the peaks of phenol, the IL concentration was estimated to be below 0.2 wt%. This is a much lower value than for instance for the HLLE system with [Hbet][Tf₂N] (14 wt%).^{10,11,32}

Finally, the dynamic viscosity η of the IL-rich phase after extraction was determined at room temperature (22 °C) as a function of the wt% of NaCl in the mixture (Fig. 3). It is evident that the viscosity of the IL-rich phase increases with increasing wt% of NaCl in the mixture. This trend can be explained by two factors: (1) the increase in the extracted Co(II) concentration in

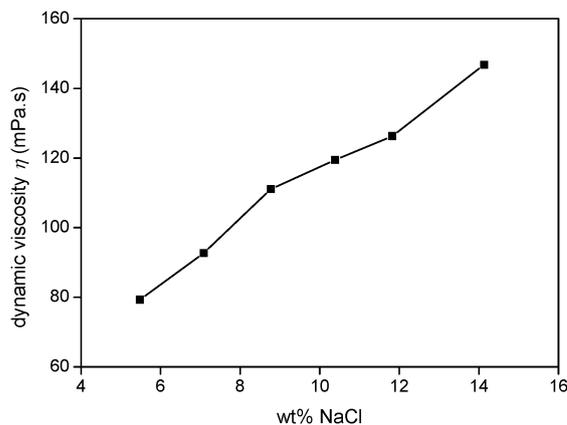


Fig. 3 Dynamic viscosity at room temperature (22 °C) of the IL-rich phase after extraction as a function of the wt% of NaCl in the extraction mixture, [Co(II)] = 1.5 g kg⁻¹, [Ni(II)] = 1.5 g kg⁻¹, and [P₄₄₄₁₄][Cl] = 40 wt%, all calculated over the entire mixture.

the IL-rich phase causes an increase in viscosity due to the formation of a divalent anion, as was described by Vander Hoogerstraete *et al.*,²⁸ and (2) the decrease in the water content of the IL-rich phase with increasing wt% of NaCl (Table 1) also results in higher viscosities. The viscosities varied around 120 mPa s at 22 °C. These values are approximately 10 times lower than the viscosities reported on the water-saturated Cyphos IL 101 system, which is around 830 mPa s at room temperature.^{27,28} This clearly indicates that viscosity problems in the extraction process, *i.e.* slow kinetics due to slow mass transport and specialized process design, are less an issue here.

In conclusion, this Communication demonstrates that the IL-ABS-HLLE system based on [P₄₄₄₁₄][Cl] and NaCl shows enhanced properties compared to conventional IL solvent extraction systems. The IL used in our system is fluorine-free and such ionic liquids are generally considered to be cheaper and more environmentally friendly than ILs containing fluorinated anions. Furthermore, the loss of IL to the aqueous phase is limited, which makes the process economically and environmentally more interesting. In addition, the most important advantage is the potentially faster extraction kinetics by application of HLLE, combined with the much lower viscosity of the IL-rich phase compared to the Cyphos IL 101 system. The low viscosity is also advantageous for process design, because high viscosities would require special pumping systems. Finally, NaCl that is added to the system is used more beneficially. In quaternary phosphonium chloride extraction systems, chloride anions need to be added to the aqueous phase anyway to achieve extraction to the IL phase. So the fact that it also induces phase separation of the hydrophilic IL means that it is not required to work with a highly hydrophobic IL such as Cyphos IL 101. Nevertheless, the IL-ABS described in this Communication still needs some improvement, including optimization of the composition of the mixture to increase the separation between Co(II) and Ni(II). Moreover, other hydrophilic ILs should be tested and compared with [P₄₄₄₁₄][Cl] and the IL-ABS-HLLE could also be applied in other metal ion separations and higher metal loadings.

This research was financially supported by the FWO-Flanders (research project G.0900.13), IWT-Flanders (PhD fellowship to BO) and KU Leuven (projects GOA/13/008 and IOF-KP RARE³). Support by IoLiTec (Heilbronn, Germany) is also gratefully acknowledged.

Notes and references

- 1 Z. Kolarik, *Solvent Extr. Ion Exch.*, 2013, **31**, 24–60.
- 2 F. Kubota and M. Goto, *Solvent Extr. Res. Dev., Jpn.*, 2006, **13**, 23–36.
- 3 I. Billard, A. Ouadi and C. Gaillard, *Anal. Bioanal. Chem.*, 2011, **400**, 1555–1566.
- 4 K. Binnemans, *Chem. Rev.*, 2007, **107**, 2592–2614.
- 5 J. F. Brennecke and E. J. Maginn, *AIChE J.*, 2001, **47**, 2384–2389.
- 6 R. D. Rogers and K. R. Seddon, *Science*, 2003, **302**, 792–793.
- 7 K. R. Seddon, *J. Chem. Technol. Biotechnol.*, 1997, **68**, 351–356.
- 8 S. Wellens, R. Goovaerts, C. Moller, J. Luyten, B. Thijs and K. Binnemans, *Green Chem.*, 2013, **15**, 3160–3164.
- 9 B. Onghena, J. Jacobs, L. Van Meervelt and K. Binnemans, *Dalton Trans.*, 2014, **43**, 11566–11578.
- 10 T. Vander Hoogerstraete, B. Onghena and K. Binnemans, *Int. J. Mol. Sci.*, 2013, **14**, 21353–21377.
- 11 T. Vander Hoogerstraete, B. Onghena and K. Binnemans, *J. Phys. Chem. Lett.*, 2013, **4**, 1659–1663.
- 12 Y. Kohno, S. Saita, Y. J. Men, J. Y. Yuan and H. Ohno, *Polym. Chem.*, 2015, **6**, 2163–2178.
- 13 R. P. Swatloski, J. D. Holbrey and R. D. Rogers, *Green Chem.*, 2003, **5**, 361–363.
- 14 D. Depuydt, L. Liu, C. Glorieux, W. Dehaen and K. Binnemans, *Chem. Commun.*, 2015, **51**, 14183–14186.
- 15 R. F. M. Frade and C. A. M. Afonso, *Hum. Exp. Toxicol.*, 2010, **29**, 1038–1054.
- 16 D. Zhao, Y. Liao and Z. Zhang, *Clean: Soil, Air, Water*, 2007, **35**, 42–48.
- 17 M. G. Freire, A. F. M. Claudio, J. M. M. Araujo, J. A. P. Coutinho, I. M. Marrucho, J. N. C. Lopes and L. P. N. Rebelo, *Chem. Soc. Rev.*, 2012, **41**, 4966–4995.
- 18 N. J. Bridges and R. D. Rogers, *Sep. Sci. Technol.*, 2008, **43**, 1083–1090.
- 19 K. E. Gutowski, G. A. Broker, H. D. Willauer, J. G. Huddleston, R. P. Swatloski, J. D. Holbrey and R. D. Rogers, *J. Am. Chem. Soc.*, 2003, **125**, 6632–6633.
- 20 M. Dilip, N. J. Bridges, H. Rodriguez, J. F. B. Pereira and R. D. Rogers, *J. Solution Chem.*, 2015, **44**, 454–468.
- 21 Y. Pei, J. Wang, L. Liu, K. Wu and Y. Zhao, *J. Chem. Eng. Data*, 2007, **52**, 2026–2031.
- 22 A. E. Visser, S. T. Griffin, D. H. Hartman and R. D. Rogers, *J. Chromatogr. B: Biomed. Sci. Appl.*, 2000, **743**, 107–114.
- 23 M. S. Alvarez, E. Gutierrez, A. Rodriguez, M. A. Sanroman and F. J. Deive, *Ind. Eng. Chem. Res.*, 2014, **53**, 8615–8620.
- 24 Y. Akama, M. Ito and S. Tanaka, *Talanta*, 2000, **53**, 645–650.
- 25 R. D. Rogers, A. E. Visser, R. P. Swatloski, D. H. Hartman and S. T. Griffin, *Abstr. Pap. Am. Chem. Soc.*, 1999, **217**, U897.
- 26 D. Dupont, D. Depuydt and K. Binnemans, *J. Phys. Chem. B*, 2015, **119**, 6747–6757.
- 27 S. Wellens, B. Thijs and K. Binnemans, *Green Chem.*, 2012, **14**, 1657–1665.
- 28 T. Vander Hoogerstraete, S. Wellens, K. Verachtert and K. Binnemans, *Green Chem.*, 2013, **15**, 919–927.
- 29 B. K. Tait, *Hydrometallurgy*, 1993, **32**, 365–372.
- 30 M. Matsumoto, A. Panigrahi, Y. Murakami and K. Kondo, *Membranes*, 2011, **1**, 98–108.
- 31 M. Atanassova, V. Mazan and I. Billard, *ChemPhysChem*, 2015, **16**, 1703–1711.
- 32 B. Onghena and K. Binnemans, *Ind. Eng. Chem. Res.*, 2015, **54**, 1887–1898.